

Cite this: *RSC Adv.*, 2015, 5, 81212Received 3rd September 2015
Accepted 18th September 2015

DOI: 10.1039/c5ra17893b

www.rsc.org/advances

Superior destabilization effects of LiBH₄ with the addition of nano-sized nickel ferrite NiFe₂O₄

Jun Zhang,^a Ping Li,^{*a} Qi Wan,^b Fuqiang Zhai,^c Alex A. Volinsky^d and Xuanhui Qu^a

The introduction of a secondary compound, known as destabilization, is an effective way to improve the desorption performance of LiBH₄. In this paper the effects of nano-sized nickel ferrite (NiFe₂O₄) on the hydrogen storage properties of LiBH₄, processed by high energy ball milling, are studied. Non-isothermal desorption results show that the onset and predominant dehydrogenation temperature of LiBH₄ + 9 mol% NiFe₂O₄ is 89 °C and 190 °C, respectively. This is 226 °C and 260 °C lower than the fusion and decomposition temperature of LiBH₄, respectively. Moreover, over 10 wt% hydrogen can be obtained by 500 °C heating, compared with 2.4 wt% for the as-received LiBH₄. Additionally, over 5 wt% hydrogen can be released at 300 °C within 20 minutes of isothermal desorption. From the X-ray diffraction results and the small area electron diffraction analysis, Fe₃O₄, NiB and Fe₃B, *in situ* formed between the reaction of LiBH₄ and NiFe₂O₄, and act to give actual destabilization effects.

1. Introduction

Hydrogen, as an eco-friendly and renewable energy carrier, is considered to be an alternative fuel for powering future vehicles.^{1–3} Since vehicles need compact, affordable and safe H₂ containment to satisfy commercial needs, conventional hydrogen storage methods, including high-pressure tanks or condensation into liquid,⁴ need to be modified to meet the increasingly demanding requirements. Therefore, this motivation has inspired scientists to research innovative hydrogen storage systems. Solid hydrogen storage materials have recently emerged as a new solution.³ Some complex hydrides, like alanates, amides and borohydrides, have recently attracted considerable attention for potential hydrogen storage due to high hydrogen reserve mass and light weight.⁵ In particular, lithium borohydrides (LiBH₄), possessing a high volumetric and gravimetric hydrogen density of 121 kg H₂ m^{−3} and 18.5 wt%,^{2,6} is highly desirable for on-board H₂ storage in fuel cell vehicles. However, unacceptable hydrogen desorption temperature⁶ (starts at around 400 °C and releases only half the hydrogen below 600 °C) and harsh re-hydrogenation conditions⁷ (at 600 °C under 350 bar H₂) inhibit its practical applications. Over the

past decades, researchers around the world have attempted numerous methods, including reacting with metal hydrides,^{8–11} restricting its particle size^{12–14} and doping with metals^{15–18} *etc.*, to improve the hydrogen storage properties of LiBH₄. Even though tremendous advances have been achieved, none of these approaches can simultaneously fulfill all of the revised US DOE's 2010 criteria¹⁹ to date.

Oxides have been commonly reported to be an effective method to enhance the hydrogen storage behaviors of LiBH₄. The early application of oxides can be dated back to 2003, when Züttel *et al.* firstly mixed LiBH₄ with SiO₂ to lower the onset desorption temperature to 200 °C, nearly a reduction of 200 °C compared with the pure LiBH₄, accompanied with 2.3 wt% H₂.⁶ Then in 2008, Yu *et al.* found that TiO₂ can significantly enhance the hydrogen properties of LiBH₄ (the initial dehydrogenation temperature at 150 °C and the majority liberation of H₂ below 220 °C), with the charge transfer between Ti and B. They also suggested that other metal oxides with variable oxidation states should also play a similar role.²⁰ After that in 2009, Yu *et al.* systematically investigated a series of oxides to find out that the order of destabilization effect for LiBH₄ was Fe₂O₃ > V₂O₅ > Nb₂O₅ > TiO₂. Though the improvements talked are encouraging, the primary desorption temperature is still too high. The reports discussed above, however, have given us a hint to search for some novel oxides, especially some metal oxides with both variable valent as well as larger Pauling's electronegativity.²¹

To the best knowledge of us, no studies have been reported on LiBH₄ doped with Ni ferrite oxide (NiFe₂O₄). Meanwhile, from Li's report,²² NiFe₂O₄ shows a remarkable improvements on LiAlH₄ with the *in situ* formed LiFeO₂ and Al–Ni compounds. Likewise, the destabilization effects of NiFe₂O₄ may also be

^aState Key Laboratory for Advanced Metals and Materials, Institute for Advanced Materials and Technology, University of Science and Technology Beijing, USTB, Beijing 100083, China. E-mail: ustbliping@126.com; Fax: +86-10-62333981; Tel: +86-10-62333981

^bEnergy Material & Technology Research Institute, General Research Institute for Nonferrous Metals, Beijing 100088, China

^cDepartament Física Aplicada, EETAC, Universitat Politècnica de Catalunya - BarcelonaTech, Castelldefels 08860, Spain

^dDepartment of Mechanical Engineering, University of South Florida, Tampa, FL 33620, USA

applicable to LiBH_4 when considering that LiBH_4 has a similar performance with LiAlH_4 . Also, Zhai *et al.* points out that MnFe_2O_4 has better effect than Fe or Mn oxides alone in improving the dehydrogenation properties of LiAlH_4 .²³ Due to the fact that Ni has a larger Pauling's electronegativity than Mn, we ultimately added NiFe_2O_4 nanoparticles to investigate their effects on the dehydrogenation performance of LiBH_4 prepared by high energy ball milling in this work.

2. Experimental details

LiBH_4 ($\geq 95\%$ pure), purchased from Acros Organics, and NiFe_2O_4 ($\geq 99.99\%$ pure, 20 nm), synthesized by the auto-combustion process (details of the synthesis process were given in the previous report²⁴), were utilized directly without any further purification. LiBH_4 doped with different mole ratios (3 mol%, 5 mol%, 7 mol%, 9 mol% and 11 mol%) of NiFe_2O_4 was ball-milled under argon atmosphere by using a QM-3B high energy mill (Nanjing NanDa Instrument Plant) at a rotating speed of 1200 rpm for 30 min. Two kinds of stainless steel balls with 4 mm and 8 mm diameters were added with a ball-to-powder weight ratio of 30 : 1. Typically, 2 g mixture was sealed in the stainless steel vessel within a high purity argon atmosphere during milling. To avoid excess heating of the stainless steel vessel, there were 10 min intervals between each 5 min milling process.

The non-isothermal and isothermal desorption were measured by using the Sieverts-type pressure-composition-temperature (P-C-T) apparatus (General Research Institute for Nonferrous Metals, China). Typically, 0.5 g sample was loaded into a stainless steel vessel and then heated from room temperature (RT) to 500 °C at a heating rate of 5 °C min⁻¹ under 0.001 MPa hydrogen pressure. It should be noted that the additional content was not taken into consideration when calculating the released hydrogen in order to make a comparison with the as-received LiBH_4 . The phase structure of the samples after milling and dehydrogenation was examined by an MXP21VAHF X-ray Diffractometer (XRD with Cu K α radiation, 40 kV, 300 mA), with the 2 θ angle ranged from 10° to 90° with a scanning rate of 10° min⁻¹. The morphology and phase constitution of all samples after ball milling and desorption were observed by field-emission scanning electron microscopy (FESEM, ZEISS ULTRA55, Germany) and transmission electron microscopy (Tecnai G2 F30 S-TWIN, FEI, USA). Simultaneous differential scanning calorimetry and mass spectrometry (DSC-MS) experiments were conducted under 50 mL min⁻¹ argon flow in a NETZSCH STA 449F3 Jupiter instrument connected to a mass spectrometer (MS, Hiden Analytical HPR-20 QMS sampling system) between 50 °C and 500 °C with a heating rate of 5 °C min⁻¹. The samples were transferred to Al_2O_3 crucibles under argon atmosphere for the DSC-MS measurements. Fourier transform infrared spectroscopy (FT-IR) analysis of the samples were carried out by using Nexus 670 FT-IR spectrometer. The FT-IR spectra were recorded from 32 scans between 500 cm⁻¹ and 3000 cm⁻¹ with a spectral resolution of 4 cm⁻¹.

All samples handling were performed under strictly inert conditions ($\geq 99.99\%$ Ar atmosphere) in the glove box

(Mikrouna, Super-750) equipped with oxygen/humidity sensors and recirculation system to avoid oxidation and moisture. Oxygen and H_2O levels were kept below 0.1 ppm.

3. Results and discussion

Fig. 1 shows the destabilizing effects of NiFe_2O_4 on LiBH_4 during non-isothermal desorption. Overall, a decrease in the onset dehydrogenation temperature and significant advance in desorption kinetics occur with the NiFe_2O_4 doping compared with the as-received LiBH_4 . Especially, the LiBH_4 + 9 mol% NiFe_2O_4 sample has an outstanding reduction in the onset desorption temperature, approximately at 89 °C, which is 226 °C lower than the as-received LiBH_4 . This shows an advance compared with previous literature reports.^{13,25} Moreover, it eventually liberates 10.75 wt% hydrogen, compared with merely 2.4 wt% for the as-received LiBH_4 . Notably, 6.6 wt% hydrogen can be obtained below 250 °C, whereas there is no apparent

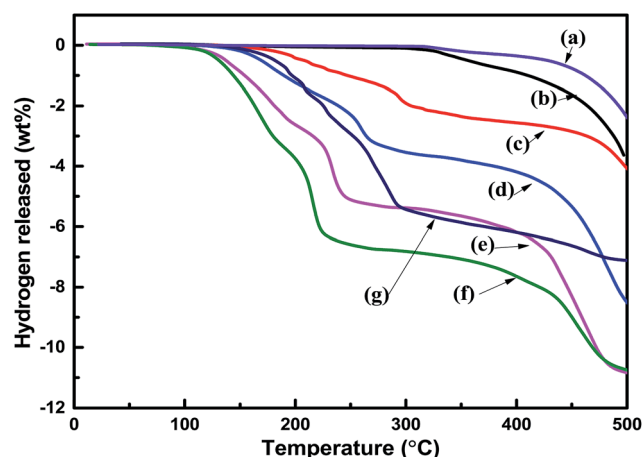


Fig. 1 Non-isothermal desorption curves of: (a) as-received LiBH_4 , (b) as-milled LiBH_4 and as-milled LiBH_4 + (c) 3 mol%, (d) 5 mol%, (e) 7 mol%, (f) 9 mol%, and (g) 11 mol% NiFe_2O_4 nanoparticles.

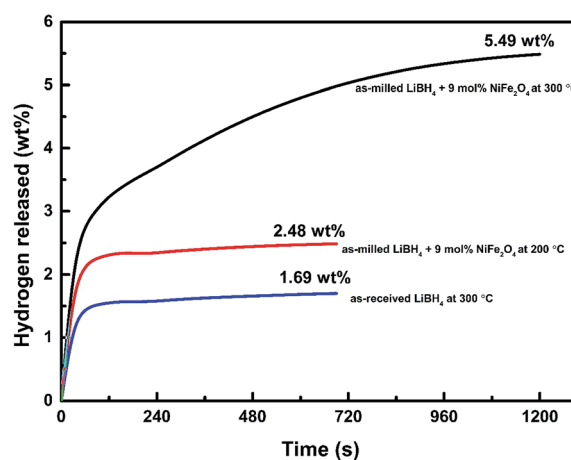


Fig. 2 Thermal desorption curves of as-received LiBH_4 and as-milled LiBH_4 + 9 mol% NiFe_2O_4 at 300 °C and 200 °C.

hydrogen release until 300 °C in the pristine LiBH_4 . It seems that the ball milling has less effect on improving the dehydrogenation performance of LiBH_4 , as only 1.2 wt% more hydrogen liberated than the as-received LiBH_4 and the initial release temperature is nearly unchanged. It can be seen from the other curves in Fig. 1 that the initial temperature falls to 136 °C, 116 °C and 88 °C for the $\text{LiBH}_4 + 3, 5, 7$ mol% NiFe_2O_4 samples, respectively. Similarly, the actual hydrogen storage capacity continues to grow, reaching 4.09, 8.52, and 10.84 wt%. On the other hand, there is one exception when the addition amounts up to 11 mol%, the destabilizing effect discussed above is less pronounced, with the onset temperature of 130 °C and 7.11 wt% of hydrogen. The rise of the initial dehydrogenation temperature and the loss of capacity may be because of excessive NiFe_2O_4 addition leading to the first dehydrogenation stage occurring during the ball milling process.

Considering kinetic properties and hydrogen capacity, the 9 mol% NiFe_2O_4 addition sample is used to analyze the destabilization effect of NiFe_2O_4 in the following tests.

Parallel to the non-isothermal analysis, the desorption kinetics at constant temperature and dynamic vacuum are also explored. The desorption characterization of the as-milled LiBH_4 is performed under the same conditions for comparison. As indicated in Fig. 2, owing to the sluggish kinetics of LiBH_4 , the as-received LiBH_4 can only release 1.46 wt% hydrogen in the first 60 seconds at 300 °C and after 12 minutes the final desorbed hydrogen is merely 1.69 wt%. It is notable that after doping with 9 mol% NiFe_2O_4 , the content of desorbed hydrogen can increase to 2.74 wt% and the ultimate hydrogen obtained is 5.49 wt% within 20 minutes. To further review this prominent effect, the temperature is lowered to 200 °C. Within 12 minutes, dehydrogenation capacity of 2.48 wt% is achieved for the $\text{LiBH}_4 + 9$ mol% NiFe_2O_4 sample. These results

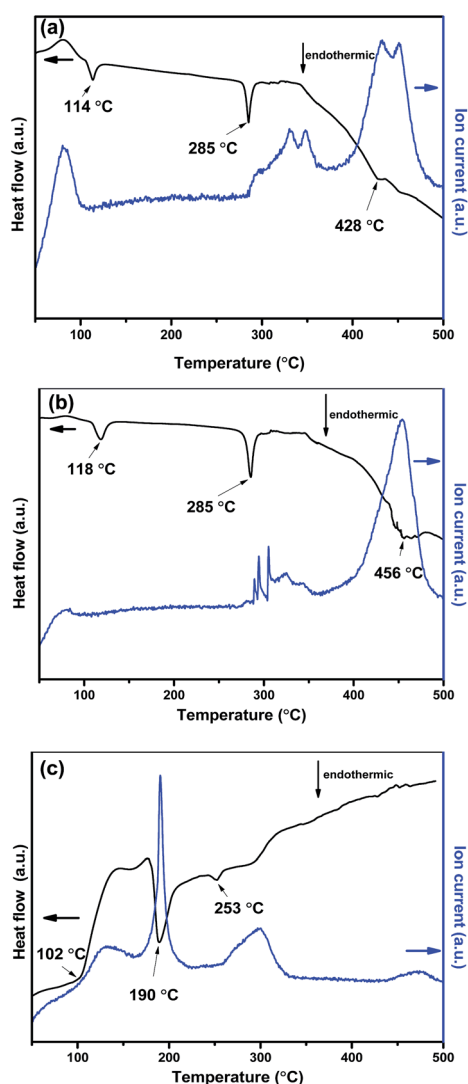


Fig. 3 DSC-MS profiles of (a) as-received LiBH_4 , (b) as-milled LiBH_4 , (c) as-milled $\text{LiBH}_4 + 9$ mol% NiFe_2O_4 at a heating rate of 5 °C min^{-1} . DSC profiles and MS spectra ($m/z = 2$) are shown as black and blue curves, respectively.

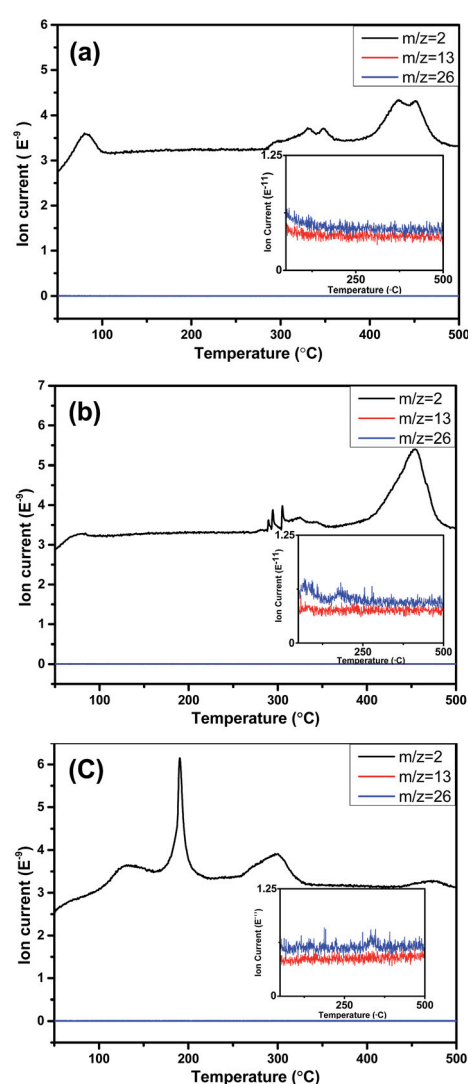


Fig. 4 Mass spectroscopy of (a): as-received LiBH_4 (b): as-milled LiBH_4 (c) as-milled $\text{LiBH}_4 + 9$ mol% NiFe_2O_4 , inset figures are magnified images of $m/z = 13$ and $m/z = 26$. $m/z = 2, 13, 26$ stands for H_2 , BH_3 , B_2H_6 .

demonstrate the NiFe_2O_4 superiority in enhancing the LiBH_4 dehydrogenation kinetics compared with previous literature reports.^{26,27}

The difference of the hydrogen capacity at the same temperature in the isothermal and non-isothermal hydrogen dehydrogenation should be ascribed to the hydrogen pressure during desorption process, as the isothermal desorption is conducted in the dynamic vacuum and the non-isothermal at hydrogen pressure of 0.001 MPa. In other words, the external hydrogen pressure may influence hydrogen liberation.²⁸ Both the non-isothermal and isothermal desorption results suggest that NiFe_2O_4 can significantly improve the dehydrogenation performance of LiBH_4 .

To reveal the reaction mechanism in the desorption process, simultaneous differential scanning calorimetry and mass spectrometry (DSC-MS) measurements are carried out (Fig. 3). In the case of pristine LiBH_4 , there are three distinct endothermic signals at 114 °C, 285 °C and 428 °C, corresponding to orthorhombic to hexagonal structure transformation, fusion and decomposition of LiBH_4 , respectively. MS results show that a small amount of hydrogen is released at 285 °C and a rapid dehydrogenation is observed at 428 °C, which is in agreement with the literature data.^{26,29,30} Although there was report³¹ showing that downsizing may have dramatic effects on thermodynamic and kinetic properties of metal hydrides, the DSC-MS profile of as-milled LiBH_4 in this study is nearly the same as the pristine LiBH_4 . It is speculated that this is because of the LiBH_4 size, which could not be decreased to the nano scale by ball milling. The slight influence of ball milling on accelerating the dehydrogenation properties of metal borohydride has also been reported in Li's study.³²

It is notable that all three endothermic events in the case of $\text{LiBH}_4 + 9 \text{ mol\% NiFe}_2\text{O}_4$ have been shifted to lower temperature compared with commercial and milled LiBH_4 . The first endothermic peak at 102 °C is related to the orthorhombic to hexagonal structure transformation. The second one, accompanied by the major liberation of hydrogen in the MS profile, is associated with the interaction between LiBH_4 and NiFe_2O_4 . The stronger and narrower hydrogen peak in the synchronous mass spectroscopy (MS) profile points to a rapid reaction. Considering the inferior amount of hydrogen and the melting temperature of commercial and as-milled LiBH_4 , the bump after the second peak at 253 °C is assigned to the residual LiBH_4 fusion. The DSC-MS results are in good agreement with the non-isothermal measurements. Other gases emitted besides hydrogen are depicted in Fig. 4. Inset figures are magnified data for BH_3 and B_2H_6 . Comparing emitted hydrogen, neither appreciable amounts of BH_3 or B_2H_6 are detected by MS during the heating process. This is encouraging, since it usually poisons the fuel cells^{33,34} and is one of the reasons for the LiBH_4 cycling capacity loss.^{35,36}

From the results discussed above, it can be seen that the decomposition behavior of $\text{LiBH}_4 + 9 \text{ mol\% NiFe}_2\text{O}_4$ is different from commercial LiBH_4 . Herein, it is imperative to ascertain the reaction mechanism. The XRD analysis is used to analyze the phase transition after ball milling and dehydrogenation. XRD patterns of the samples after ball milling are shown in Fig. 5, along with commercial LiBH_4 for comparison. For commercial LiBH_4 , there are no other peaks found, except those belonging to LiBH_4 . As for the as-milled LiBH_4 , the peaks of LiBH_4 are relatively broadened due to the reduction in particle size. There are no visible diffraction peaks of LiBH_4 in the pattern of as-

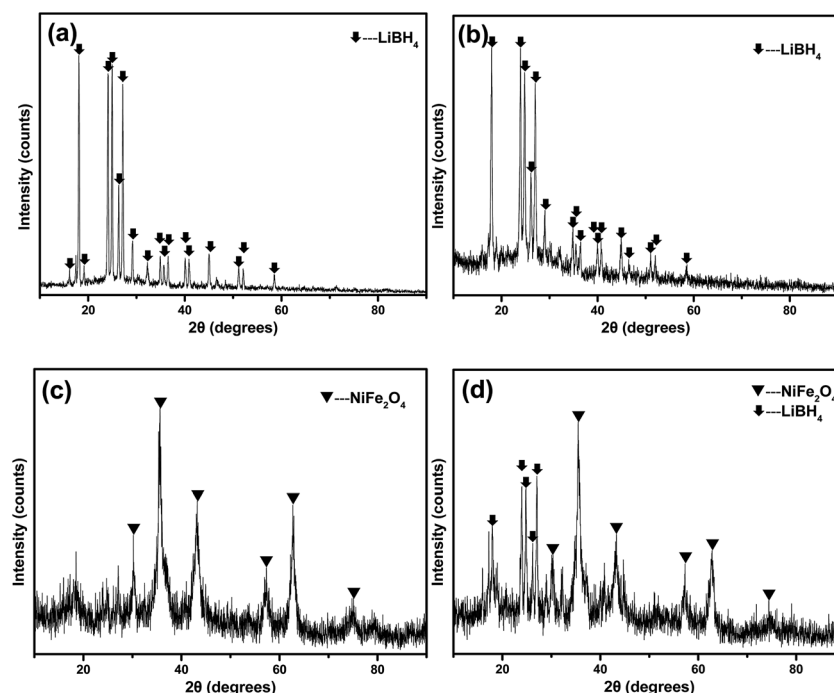


Fig. 5 XRD patterns after high energy ball milling: (a) as-received LiBH_4 , (b) as-milled LiBH_4 , (c) as-milled $\text{LiBH}_4 + 9 \text{ mol\% NiFe}_2\text{O}_4$ (d) as-milled $\text{LiBH}_4 + 3 \text{ mol\% NiFe}_2\text{O}_4$.

milled $\text{LiBH}_4 + 9 \text{ mol\% NiFe}_2\text{O}_4$. To identify whether this is ascribed to the NiFe_2O_4 addition, XRD study of $\text{LiBH}_4 + 3 \text{ mol\% NiFe}_2\text{O}_4$ is conducted, as shown in Fig. 5(d). Although the diffraction peaks of LiBH_4 are visible in $\text{LiBH}_4 + 3 \text{ mol\% NiFe}_2\text{O}_4$, their intensity is weaker than the as-milled LiBH_4 . This means that the incremental content of NiFe_2O_4 causes gradual decrease in the intensity of LiBH_4 diffraction peaks and increases the degree of LiBH_4 amorphization.²¹ It seems that there is no detectable reaction between LiBH_4 and NiFe_2O_4 during the milling process, since no other phases are identified except for LiBH_4 and NiFe_2O_4 .

Fig. 6 shows the XRD patterns of the samples after dehydrogenation. Interestingly, for the pure LiBH_4 after dehydrogenation, the LiBH_4 peaks are still observed. However, this is reasonable if sluggish LiBH_4 kinetics is considered, since only 2.4 wt% hydrogen is released when heated to 500 °C. In addition to LiBH_4 , LiH and LiBO_2 are also detected, where LiH phases are produced from the decomposition of LiBH_4 , while LiBO_2 phases come from the air contamination during measurements. In the

case of $\text{LiBH}_4 + 9 \text{ mol\% NiFe}_2\text{O}_4$ sample, there are new diffraction peaks of LiBO_3 , NiB , Fe_3O_4 , and Fe_3B phases, caused by the interaction between LiBH_4 and NiFe_2O_4 during the dehydrogenation process. As Shan *et al.*³⁷ mentioned, most transition metal catalysts need electrons to occupy the 3d orbit, and B has only one electron in the 2p orbit, while Fe and Ni have 6 and 8 electrons in the 3d orbit. Therefore, it is more feasible for B to provide an electron to Fe and Ni, achieving a more stable state. Herein, it is speculated that the destabilization effect of NiFe_2O_4 comes from the synergetic effects of NiB , Fe_3O_4 and Fe_3B .

Because of the limitations of XRD technique to detect amorphous or low content phases, Fourier transform infrared spectroscopy (FT-IR) is adopted to further reveal the reaction mechanism during the milling and de/re-hydrogenation process, as depicted in Fig. 7(a) and (b). Meanwhile, some dashed lines are added in Fig. 7 in order to better compare the peaks.

As seen in Fig. 7(a), as-received LiBH_4 exhibits the characteristic peaks of B–H stretching at 2387 cm^{-1} , 2295 cm^{-1} and

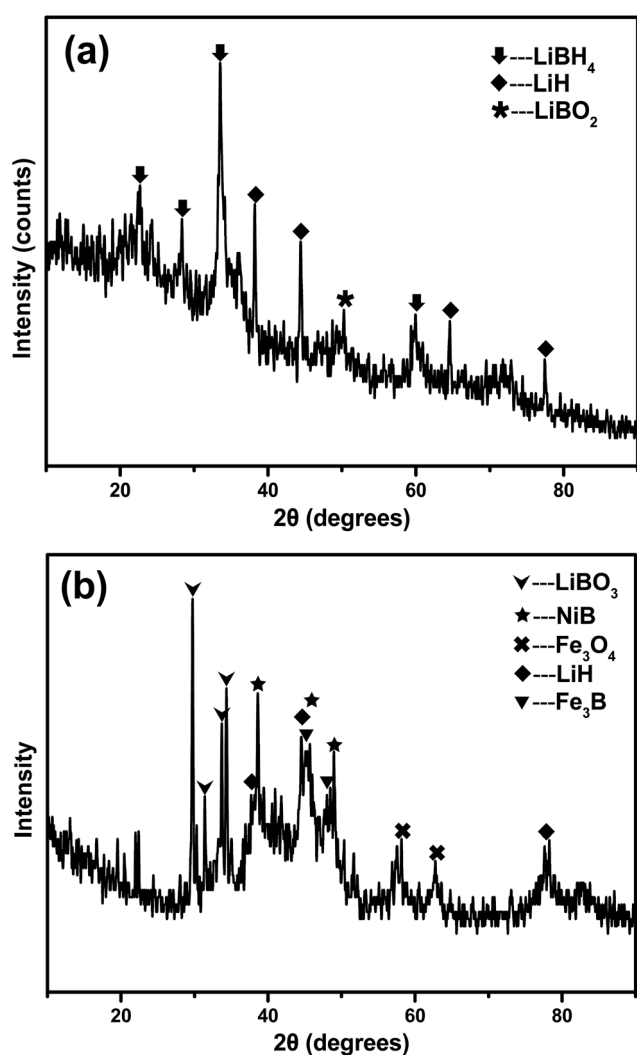


Fig. 6 XRD patterns of the samples after dehydrogenation: (a) as-received LiBH_4 and (b) as-milled $\text{LiBH}_4 + 9 \text{ mol\% NiFe}_2\text{O}_4$.

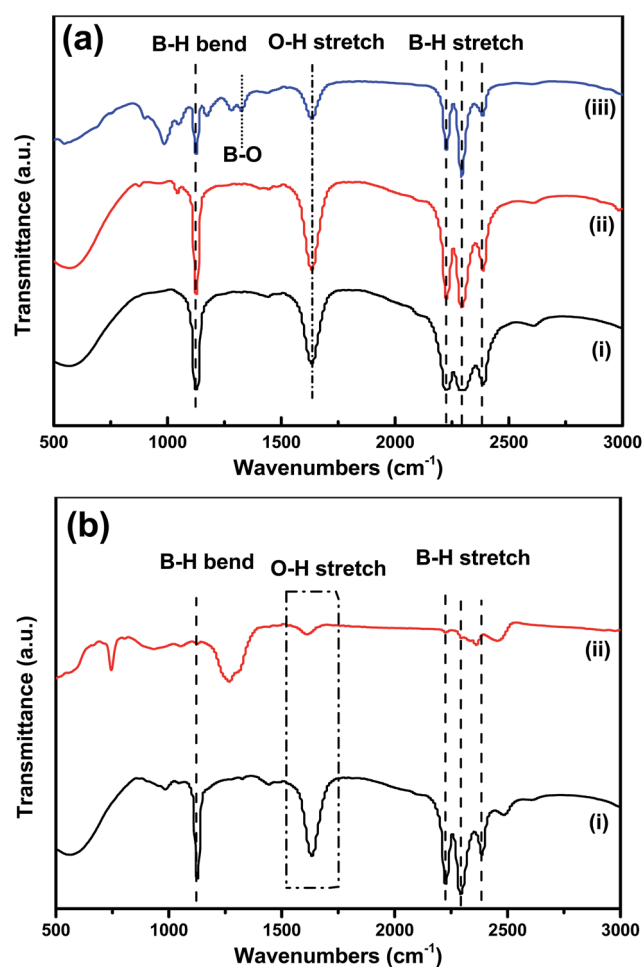


Fig. 7 FT-IR spectra of (a): after milling (i) as-received LiBH_4 , (ii) as-milled LiBH_4 , (iii) as-milled $\text{LiBH}_4 + 9 \text{ mol\% NiFe}_2\text{O}_4$ and (b) after dehydrogenation (i) as-milled LiBH_4 (ii) as-milled $\text{LiBH}_4 + 9 \text{ mol\% NiFe}_2\text{O}_4$.

2225 cm^{-1} , and B–H bending at 1126 cm^{-1} .^{21,26,30,38,39} The peak at 1633 cm^{-1} corresponds to O–H stretches, which may be related to the moisture contamination during examinations^{13,14} and the hygroscopicity of KBr (even when dehydrated).^{25,27,40} The shape of the as-milled LiBH_4 spectrum is the same as the pristine one, indicating that LiBH_4 phases remain stable during the ball milling process.

As for the LiBH_4 sample milled with 9 mol% NiFe_2O_4 , the characteristic B–H peaks remain, but with some new subtle peaks at 985 cm^{-1} , 1173 cm^{-1} , 1281 cm^{-1} and 1325 cm^{-1} . The peak at 1281 cm^{-1} is B–H,³⁰ which cannot be observed in the commercial LiBH_4 , suggesting some other LiBH_4 phases. The peak at 1325 cm^{-1} is assigned to the vibration modes of the B–O bonds,⁴¹ pointing to partial interaction between NiFe_2O_4 and LiBH_4 during the milling process.

With respect to the samples after dehydrogenation in Fig. 7(b), one can also find the same B–H peaks remaining in the case of as-received LiBH_4 , compared to that before dehydrogenation, which further validates the XRD results. When it comes to the LiBH_4 + 9 mol% NiFe_2O_4 sample after dehydrogenation, it is found that all characteristic peaks of B–H stretching at 2387 cm^{-1} , 2295 cm^{-1} and 2225 cm^{-1} and B–H bending at 1126 cm^{-1} disappear, suggesting that LiBH_4 is completely decomposed. The fresh peaks at 745 cm^{-1} and 2455 cm^{-1} are attributed to $[\text{B}_{12}\text{H}_{12}]^{-1}$, indicating LiBH_4 decomposition into $\text{Li}_2\text{B}_{12}\text{H}_{12}$.²⁸ The FT-IR results confirm that NiFe_2O_4 can facilitate the decomposition of LiBH_4 . Additionally, there is a partial reaction between LiBH_4 and NiFe_2O_4 during the ball milling process and LiBH_4 is partially reversed after the addition of NiFe_2O_4 .

For better understanding of the potential destabilization mechanism, field scanning electron microscopy (FESEM) observations are conducted. Fig. 8 depicts FESEM images of the

as-received, as-milled LiBH_4 and as-milled LiBH_4 + 9 mol% NiFe_2O_4 . Prior to ball milling, the particle size of LiBH_4 ranges from 1 μm to 5 μm irregularly, posing a disadvantage to the dehydrogenation kinetics. For the commercial LiBH_4 after ball milling, the particles become much smaller, forming clusters, which also block rapid dehydrogenation. However, after ball milling with NiFe_2O_4 , as shown in Fig. 8(c), the particle size declines to 300 nm and 800 nm, and the distribution of these particles become more uniform. This may be one of reasons for the enhancement of dehydrogenation kinetics, as these nano-sized particles may serve as the nucleation sites. One thing should be noted that the embedded NiFe_2O_4 cannot be seen in the LiBH_4 matrix owing to its nano particle size.

From the above analysis, the superior destabilizing effects may result from the ball milling with NiFe_2O_4 , leading to the significant LiBH_4 particle size decline.

Since the NiFe_2O_4 nanoparticles could not be observed by FESEM, it is imperative to observe the nanostructure of un-doped and doped sample to further demonstrate the superior effects of nano-sized NiFe_2O_4 . Fig. 9 shows dark field images, HRTEM and EDX analyses in the as-milled LiBH_4 + 9 mol% NiFe_2O_4 sample. In Fig. 9(a) some black particles are homogeneously distributed among the grey matrix. To figure out what these particles are, corresponding EDX measurements of the black area A and the grey area B are conducted, as shown in Fig. 9(c) and (d), respectively. For the black area, O, Fe, Ni and Cu elements are identified (Cu comes from the sample holder). Although Fe and Ni elements are detected in the grey area, their intensity is much weaker than in the black area. It must be pointed out that EDX cannot reliably detect LiBH_4 due to the weak scattering of electrons by the light Li, B and H elements. Thus, it could be said that the black nanoparticles correspond to NiFe_2O_4 , while the grey correspond

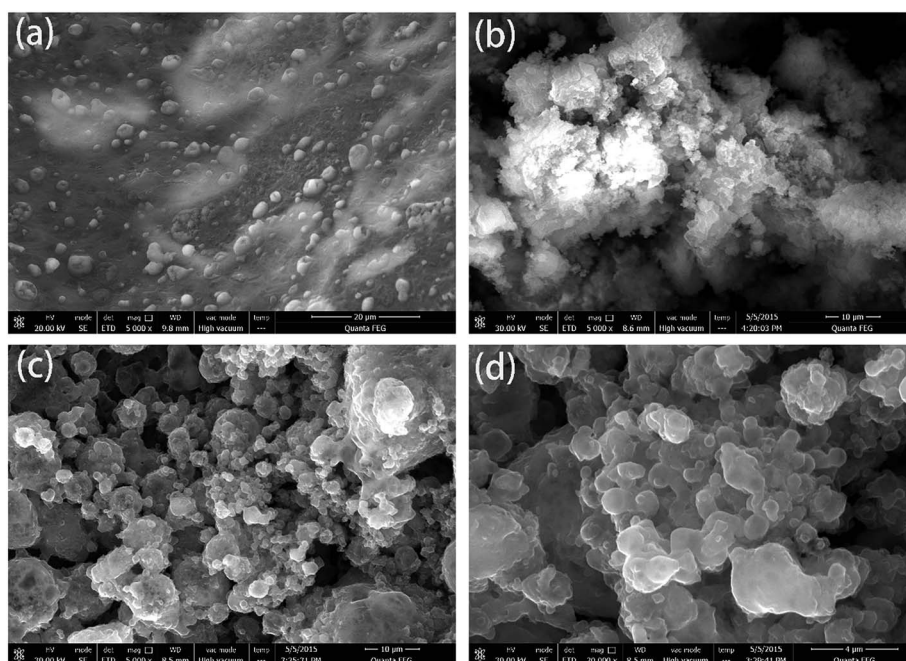


Fig. 8 FESEM images of (a) as-received LiBH_4 (b) as-milled LiBH_4 (c) as-milled LiBH_4 + 9 mol% NiFe_2O_4 and (d) is magnified image of (c).

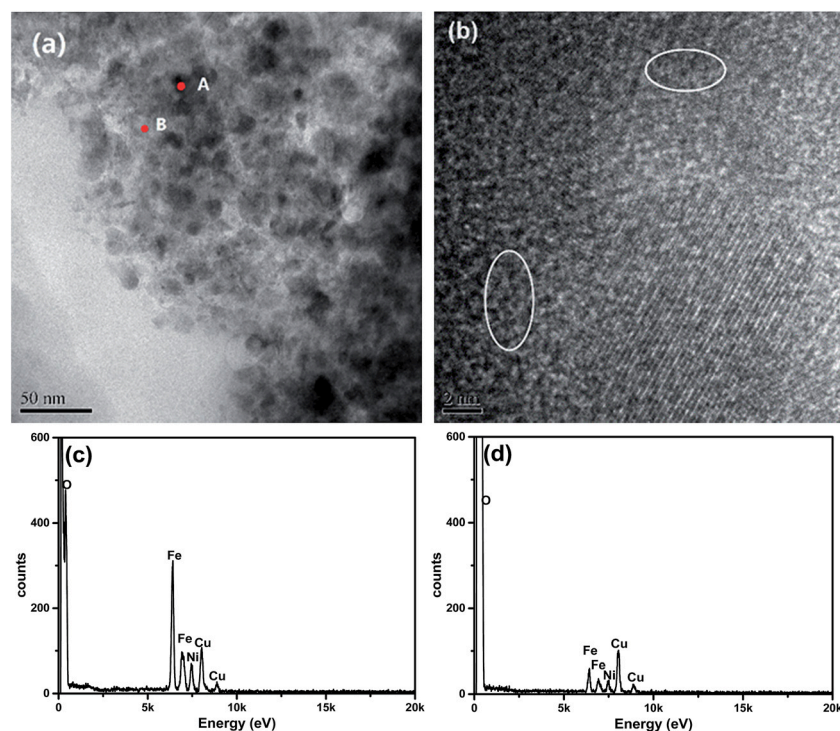


Fig. 9 (a) TEM images and (b) HRTEM images of boundaries micrographs of black and grey regions. EDX: (c) black region and (d) grey region are results of as-milled $\text{LiBH}_4 + 9 \text{ mol\% NiFe}_2\text{O}_4$.

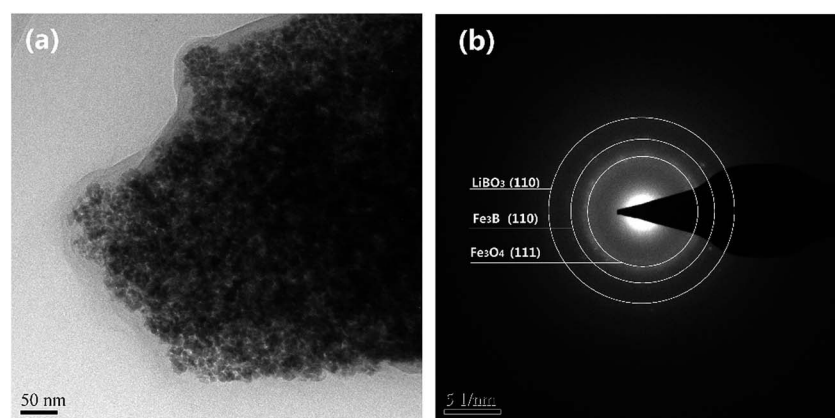


Fig. 10 (a) TEM micrograph and (b) corresponding SAED pattern of as-milled $\text{LiBH}_4 + 9 \text{ mol\% NiFe}_2\text{O}_4$ after dehydrogenation.

to LiBH_4 . It can be concluded that the NiFe_2O_4 nanoparticles are homogeneously embedded in the LiBH_4 matrix after ball milling, improving rapid dehydrogenation kinetics.

LiBH_4 is detected by the FT-IR measurements, but not XRD, which was previously attributed to the amorphous state of LiBH_4 after ball milling with NiFe_2O_4 . To demonstrate this, HRTEM images were obtained. As expected, there is some amorphization in the oval area, which is consistent with the FT-IR results and XRD analysis. The electron micrograph of dehydrogenated $\text{LiBH}_4 + 9 \text{ mol\% NiFe}_2\text{O}_4$ is shown in Fig. 10(a), which looks similar to the as-milled sample with some nanoparticles spread evenly among the grey areas. To further investigate the microstructure of $\text{LiBH}_4 + 9 \text{ mol\% NiFe}_2\text{O}_4$, selected

area electronic diffraction (SAED) results are shown in Fig. 10(b). The dim lattice diffraction pattern indicates that there is a high degree of amorphization, which can also be demonstrated by the broader XRD reflections. Additionally, the existence of Fe_3B and Fe_3O_4 phases are proven by the SAED measurements.

4. Conclusions

In this paper, it is found the nano-sized nickel ferrite (NiFe_2O_4) can effectively destabilize LiBH_4 . According to the non-isothermal and isothermal desorption results, it liberates hydrogen at 89°C and the hydrogen capacity is 10.75 wt% and

one could get 5.49 wt% in just 20 minutes. In comparison with the raw LiBH_4 , this is a huge advance. The mass spectroscopy detect neither BH_3 nor B_2H_6 , which poison the fuel cells and can often lead to H_2 capacity loss, other than pure hydrogen. The XRD patterns combined with the SAED measurements uncover the existence of the Fe_3B , NiB and Fe_3O_4 , which show a synergistic effect on accelerating the dehydrogenation properties of LiBH_4 . The FT-IR results reveal that the addition of NiFe_2O_4 leads to the complete decomposition of LiBH_4 when heated to 500°C , while there is still a big surplus of LiBH_4 for the undoped one. The FESEM figures indicate that the particle size of LiBH_4 declines significantly after ball milling with NiFe_2O_4 .

Acknowledgements

This study was supported by the Beijing Natural Science Foundation (2152019), and the National Natural Science Foundation of China (Grant No. 51471054). Fuqiang Zhai thanks the China Scholarship Council (CSC) for providing the scholarship.

References

- 1 J. Yang and S. Hirano, *Adv. Mater.*, 2009, **21**, 3023–3028.
- 2 L. Schlapbach and A. Züttel, *Nature*, 2001, **414**, 353–358.
- 3 J. Yang, A. Sudik, C. Wolverton and D. J. Siegel, *Chem. Soc. Rev.*, 2010, **39**, 656–675.
- 4 I. P. Jain, *Int. J. Hydrogen Energy*, 2009, **34**, 7368–7378.
- 5 S.-I. Orimo, Y. Nakamori, J. R. Eliseo, A. Züttel and C. M. Jensen, *Chem. Rev.*, 2007, **107**, 4111–4132.
- 6 A. Züttel, P. Wenger, S. Rentsch, P. Sudan, P. Mauron and C. Emmenegger, *J. Power Sources*, 2003, **118**, 1–7.
- 7 S.-I. Orimo, Y. Nakamori, G. Kitahara, K. Miwa, N. Ohba, S.-I. Towata and A. Züttel, *J. Alloys Compd.*, 2005, **404**, 427–430.
- 8 P. Sridechprasat, Y. Suttisawat, P. Rangsunvigit, B. Kitiyanan and S. Kulprathipanja, *Int. J. Hydrogen Energy*, 2011, **36**, 1200–1205.
- 9 L. A. Zeng, H. Miyaoka, T. Ichikawa and Y. Kojima, *J. Phys. Chem. C*, 2010, **114**, 13132–13135.
- 10 F. E. Pinkerton, M. S. Meyer, G. P. Meisner, M. P. Balogh and J. J. Vajo, *J. Phys. Chem. C*, 2007, **111**, 12881–12885.
- 11 D. M. Liu, W. J. Huang, T. Z. Si and Q. A. Zhang, *J. Alloys Compd.*, 2013, **551**, 8–11.
- 12 S. D. House, X. Liu, A. A. Rockett, E. H. Majzoub and I. M. Robertson, *J. Phys. Chem. C*, 2014, **118**, 8843–8851.
- 13 R. Goslawit-Utke, S. Meethom, C. Pistidda, C. Milanese, D. Laipple, T. Saisopa, A. Marini, T. Klassen and M. Dornheim, *Int. J. Hydrogen Energy*, 2014, **39**, 5019–5029.
- 14 T. Sun, J. Liu, Y. Jia, H. Wang, D. Sun, M. Zhu and X. Yao, *Int. J. Hydrogen Energy*, 2012, **37**, 18920–18926.
- 15 P. Ngene, M. H. W. Verkuijlen, Q. Zheng, J. Kragten, P. J. M. van Bentum, J. H. Bitter and P. E. de Jongh, *Faraday Discuss.*, 2011, **151**, 47.
- 16 D. Blanchard, Q. Shi, C. Boothroyd and T. Vegge, *J. Phys. Chem. C*, 2009, **113**, 14059–14066.
- 17 X.-D. Kang, P. Wang, L.-P. Ma and H.-M. Cheng, *Appl. Phys. A: Mater. Sci. Process.*, 2007, **89**, 963–966.
- 18 E. Callini, A. Borgschulte, C. L. Hugelshofer, A. J. Ramirez-Cuesta and A. Züttel, *J. Phys. Chem. C*, 2014, **118**, 77–84.
- 19 T. J. Frankcombe, *Chem. Rev.*, 2012, **112**, 2164–2178.
- 20 X. B. Yu, D. A. Grant and G. S. Walker, *J. Phys. Chem. C*, 2008, **112**, 11059–11062.
- 21 W. Cai, H. Wang, D. Sun, Q. Zhang, X. Yao and M. Zhu, *RSC Adv.*, 2014, **4**, 3082.
- 22 P. Li, Z. Li, F. Zhai, Q. Wan, X. Li, X. Qu and A. A. Volinsky, *J. Phys. Chem. C*, 2013, **117**, 25917–25925.
- 23 F. Zhai, P. Li, A. Sun, S. Wu, Q. Wan, W. Zhang, Y. Li, L. Cui and X. Qu, *J. Phys. Chem. C*, 2012, **116**, 11939–11945.
- 24 P. Li, Q. Wan, Z. L. Li, F. Q. Zhai, Y. L. Li, L. Q. Cui, X. H. Qu and A. A. Volinsky, *J. Power Sources*, 2013, **239**, 201–206.
- 25 L. Guo, L. Jiao, L. Li, Q. Wang, G. Liu, H. Du, Q. Wu, J. Du, J. Yang, C. Yan, Y. Wang and H. Yuan, *Int. J. Hydrogen Energy*, 2013, **38**, 162–168.
- 26 J. Shao, X. Xiao, X. Fan, L. Zhang, S. Li, H. Ge, Q. Wang and L. Chen, *J. Phys. Chem. C*, 2014, **118**, 11252–11260.
- 27 Y. Zhao, L. Jiao, Y. Liu, L. Guo, L. Li, H. Liu, Y. Wang and H. Yuan, *Int. J. Hydrogen Energy*, 2014, **39**, 917–926.
- 28 Y. Yan, A. Remhof, S. J. Hwang, H. W. Li, P. Mauron, S. Orimo and A. Züttel, *Phys. Chem. Chem. Phys.*, 2012, **14**, 6514–6519.
- 29 C. Frommen, M. Heere, M. D. Riktor, M. H. Sørby and B. C. Hauback, *J. Alloys Compd.*, 2015, **645**, S155–S159.
- 30 J. Chen, T. He, G. Wu, Z. Xiong, L. Liu, X. Ju and P. Chen, *J. Phys. Chem. C*, 2014, **118**, 13451–13459.
- 31 T. K. Nielsen, U. Bosenberg, R. Goslawit, M. Dornheim, Y. Cerenius, F. Besenbacher and T. R. Jensen, *ACS Nano*, 2010, **4**, 3903–3908.
- 32 H. W. Li, K. Kikuchi, Y. Nakamori, K. Miwa, S. Towata and S. Orimo, *Scr. Mater.*, 2007, **57**, 679–682.
- 33 X. Si, F. Li, L. Sun, F. Xu, S. Liu, J. Zhang, M. Zhu, L.-Z. Ouyang, D. Sun and Y.-L. Liu, *J. Phys. Chem. C*, 2011, **115**, 9780–9786.
- 34 R. Goslawit-Utke, J. M. B. von Colbe, M. Dornheim, T. R. Jensen, Y. Cerenius, C. B. Minella, M. Peschke and R. Bormann, *J. Phys. Chem. C*, 2010, **114**, 10291–10296.
- 35 X. Liu, D. Peaslee, C. Z. Jost, T. F. Baumann and E. H. Majzoub, *Chem. Mater.*, 2011, **23**, 1331–1336.
- 36 B. J. Zhang and B. H. Liu, *Int. J. Hydrogen Energy*, 2010, **35**, 7288–7294.
- 37 J. Shan, P. Li, Q. Wan, F. Zhai, J. Zhang, Z. Li, Z. Liu, A. A. Volinsky and X. Qu, *J. Power Sources*, 2014, **268**, 778–786.
- 38 P. Javadian, D. A. Sheppard, C. E. Buckley and T. R. Jensen, *Nano Energy*, 2015, **11**, 96–103.
- 39 B. J. Zhang, B. H. Liu and Z. P. Li, *J. Alloys Compd.*, 2011, **509**, 751–757.
- 40 M. P. Pitt, M. Paskevicius, D. H. Brown, D. A. Sheppard and C. E. Buckley, *J. Am. Chem. Soc.*, 2013, **135**, 6930–6941.
- 41 B. M. Concha, M. Chatenet, F. Maillard, E. A. Ticianelli, F. H. Lima and R. B. de Lima, *Phys. Chem. Chem. Phys.*, 2010, **12**, 11507–11516.